

# Synthesis and Characterisation

*by* Dyah Suci Perwitasari

---

**Submission date:** 08-Jan-2021 12:35PM (UTC+0700)

**Submission ID:** 1484437324

**File name:** DYAH\_Synthesis\_and\_Characterisation\_of\_Struvite\_Family\_\_1.pdf (227.64K)

**Word count:** 3212

**Character count:** 17238

7

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/303499221>

# Synthesis and Characterisation of Struvite Family Crystals by An Aqueous Precipitation Method

Article in MATEC Web of Conferences · January 2016

DOI: 10.1051/mateconf/20165801006

CITATIONS

3

READS

543

6 authors, including:



Stefanus Muryanto  
Universitas 17 Agustus 1945 Semarang

77 PUBLICATIONS 120 CITATIONS

[SEE PROFILE](#)



Jamari Jamari  
Universitas Diponegoro

168 PUBLICATIONS 394 CITATIONS

[SEE PROFILE](#)

Some of the authors of this publication are also working on these related projects:



Running-in of Rolling-sliding Contacts [View project](#)



The influence of tool path strategies on surface roughness and machining time in the CNC milling of UHMWPE [View project](#)

7

All content following this page was uploaded by Stefanus Muryanto on 13 June 2016.

The user has requested enhancement of the downloaded file.

## SYNTHESIS AND CHARACTERISATION OF STRUVITE FAMILY CRYSTALS BY AN AQUEOUS PRECIPITATION METHOD

S.Sutiyono<sup>1</sup>, Luluk Edahwati<sup>1,2</sup>, Dyah Suci Perwitasari<sup>1,2</sup>,  
Stefanus Muryanto<sup>2,3</sup>, J. Jamari<sup>2</sup> and Anatasius P.Bayuseno<sup>2</sup>

<sup>1</sup>Department of Chemical Engineering, University of Pembangunan Nasional "Veteran" Jatim.

<sup>2</sup>Center for Waste Management, Mechanical Engineering Graduate Program,  
Diponegoro University, Tembalang Campus, Semarang 50275, Indonesia.

<sup>2,3</sup>Office of Research and Department of Chemical Engineering, UNTAG, Bendhan Dhuwur Campus, Semarang 50233,  
Indonesia.

E-mail: [apbayuseno@gmail.com](mailto:apbayuseno@gmail.com)

### 32 STRACT

Struvite ( $\text{NH}_4\text{MgPO}_4 \cdot 6\text{H}_2\text{O}$ ) is a mineral often found as a scale deposit in an industrial process and piping. The common occurrence of struvite formation is a wide variety of environments. pH solution and environmental temperature are important parameters that control precipitation and subsequent decomposition of struvite. The study aims to characterise the struvite precipitated out the solution through chemical and mineralogical analysis. In this work, struvite solution was prepared by mixing  $\text{NH}_4\text{OH}$ ,  $\text{MgCl}_2$  and  $\text{H}_3\text{PO}_4$  with the different purity grade (A and B) in the mol ratio of 1 : 1 : 1 in the stirred glass vessel tank with volume of 500 ml, and then stirred at 200 rpm for 70 minutes. Temperature of 30 °C and an initial pH of 10 were selected. The precipitated deposit was dried at room temperature for 48 hours of being analyzed. Material characterization of the deposits was conducted using XRPD Rietveld method of qualitative and quantitative mineralogical phase analysis. XRF was employed for bulk chemical elemental analysis of the scale obtained. The sample A using analytical grade powder provided the major phases of struvite-(K) and struvite. In contrast, the major phase of newberyite and minor phases of lepidocrocite ( $\text{FeOOH}$ ) and niter ( $\text{KNO}_3$ ) was observed by following changes in the lowest purity of powder (Sample B). Analysis of the experimental data suggests a solution mediated transformation process as a possible mechanism of struvite transformation.

**Keywords:** Bulk elemental analysis; Characterization; Struvite scalling, XRPD Rietveld method

### INTRODUCTION

Struvite ( $\text{NH}_4\text{MgPO}_4 \cdot 6\text{H}_2\text{O}$ ) or magnesium ammonium phosphate (MAP) is a mineral often found as a precipitate in an industrial process and pipping system. Struvite precipitated in wastewater treatment plants make some problems causing deposits in pipe walls [Gaterell *et al.*, 2000; Priestley *et al.*, 1997]. It is also known as a bio-mineral in urinary tracts and kidney. However, precipitation of struvite has been addressed as a recovery method of ammonia or phosphate from industrial and domestic wastewaters [Tünay *et al.*, 1997; Shin and Lee, 1997; Schulze-Rettmer, 1991; Snoeying and Jenkins, 1980; Loewenthal *et al.*, 1994]. It has attracted considerable attention because of its occurrence of different environments and its utility as a resource. Struvite has been reported to be a highly effective source of nitrogen, magnesium and phosphorus for plants and can be used as a slow release fertilizer at high application rates without damaging plant roots [Whitaker and Jeffery, 1970; Battistoni *et al.*, 1997; 2000].


Struvite precipitation may be controlled by an alkali pH levels and temperatures. Moreover, struvite

decomposition occurs to a slow low heating, while this decomposition is accompanied by developing both ammonia and water at temperatures below 40°C. However, more rapid heating enables the decomposition to occur at around 80°C. Thus synthesis route of minerals from struvite-saturated solutions may be carried at high temperature due to the increasing solubility of struvite.

Further, in the air, struvite may transform to form dittmarite ( $\text{MgNH}_4\text{PO}_4 \cdot \text{H}_2\text{O}$ ) at 103 °C [Abdelrazig and Sharp, 1988], but in water, it decomposes slightly at lower temperature of 60 °C [Sarkar, 1991]. Additionally, the remaining water of crystallisation and  $\text{NH}_4$  are liberated at 235 °C and followed by formation of the pyrophosphate at 575 C [Abdelrazig and Sharp, 1983]. Here, magnesium pyrophosphate is considered as the most stable phase at high temperature. However, the different minerals may be produced in-between temperature. The stable temperature range of struvite decomposition may be related to the occurring process in the presence of nitrogen, air, or water [Frost *et al.*, 2004]. In turn, the presence of water enables the stable temperature range of the generated minerals to lower values. Thus, this conditional process can provide important


information about the possible resulting minerals from struvite-saturated solutions to elevated

Struvite precipitation occurs to the presence of  $Mg^{+2}$  (M),  $NH_4^+$  (N) and  $PO_4^{3-}$  (P) and the thermodynamic solubility product,  $K_s$ , is surpassed according to following reaction:



$$K_s = [Mg^{2+}][NH_4^+][PO_4^{3-}] \quad (2)$$

However, the precipitation of struvite has been reported to reduce with the pH, in which  $HPO_4^{2-}$  is predominantly precipitated in the reaction instead of  $PO_4^{3-}$  according to following reaction:



Struvite crystals have been reported to be formed in the pH range of 7-11. In this range pH, a few crystals may be formed including trimagnesium phosphate  $[Mg_3(PO_4)_2 \cdot 6H_2O]$ , newberyite  $[MgHPO_4 \cdot 3H_2O]$ , and bobierrite  $[Mg_3(PO_4)_2 \cdot 8H_2O]$  [Musvoto et al., 2000]. Here, the solution pH and concentration of magnesium and phosphate controls the formation of these crystals.

The present study was undertaken to examine temperature and pH on struvite crystallization. The emphasis of this study was to synthesize struvite crystals and discuss the impact on the quality of the recovered product. The degree of **28** stallization for struvite products was analyzed by the Rietveld refinement method of x-ray powder diffraction (XRPD). Total elemental composition of solid crystals was conducted by wavelength dispersive X-ray fluorescence (XRF).

## METHODOLOGY

### Sample preparation

Struvite precipitation experiments were carried out in a batch reactor with a volume of 500 ml mixed with magnetic stirrer. The pH measurements are made with pH meter E588 Metrohm Herisau and pH is adjusted by KOH solutions. The chemicals used for synthesis were technical and analytical grade and hereby designated as sample A and B. In this work, struvite solution was prepared by mixing  $NH_4OH$ ,  $MgCl_2$  and  $H_3PO_4$  in the mol ratio of 1:1:1

temperature. But it cannot be used to predict the mineral formation of the solution.

and then stirred at 200 rpm for 70 minutes. Temperature of 30 °C and an initial pH of 10 were adjusted. The precipitated deposit was dried at room temperature for 48 hours of being analysed.

### Bulk chemical analysis

X-ray fluorescence (XRF) was employed for measurement of total elemental chemistry (mass of element/dry mass of solid crystal) with lower detection limits (LDL)- down to a few ppm (order of less than 10 ppm) for all size fractions (<100 µm) of the solid crystals. Further, batches of 8 grams of the sample were mixed with 2 g of acetone as a binder. The acetone was employed to increase sample densification. The mixture was finely homogenised in an agate bowl. The powder pellets were subsequently pressed on 20 Kg/cm<sup>2</sup> for 2 minutes and finally analyzed by XRF for all elements present in the solid, except for those lighter than fluorine (atomic mass=19).

### X-ray powder diffraction (XRPD) and Rietveld analysis

XRPD measurements were conducted on A Philips PW 1710 Diffractometer equipped with a Cu tube and measurement parameters: 40 kV, 40 mA, 0.02° step, 2 s per step, 5 – 90° 2θ. Phase identification was made with (Powder Diffraction File)-PDF-2 Phillips software. Rietveld refinement of the XRPD data was carried out with Program Fullprof-2k, version 3.30 [Rodriguez-Carvajal, 2005], with the crystal structure database from the published data in Mineralogical Society of America (see Table 1). Results presented here were obtained with refining fundamental parameters such as: the 2θ scale zero position, the polynomial fitting for the background with six coefficients, the phase scale factors, the cell parameters, the peak asymmetry and the peak shape functions, the atomic coordinates, anisotropic temperature factors, and the preferred orientation for struvite family crystal with March-model. Site occupation factors were not refined during Rietveld refinement, because of all struvite peaks are overlapped by peaks of other minerals. The error of the Rietveld quantifications can be estimated to about 2 wt. % (1p) per phase.

**1**  
**Table-1.** Crystal structure models used in Rietveld refinements

Structure models	PDF number	Authors
Struvite [MgNH <sub>4</sub> PO <sub>4</sub> •6H <sub>2</sub> O]	PDF#71-2089	Whitaker and Jeffery (1970)
Stuvite-(K) [KMgPO <sub>4</sub> •6H <sub>2</sub> O]	PDF#35-0812	Graeser et al. (2008)
Newberyite [MgHPO <sub>4</sub> •3H <sub>2</sub> O]	PDF# 76-3368	Abbona et al. (1979)
Lepidocrocite [FeOOH]	PDF#89-6096	Pernet, Joubert, Berthet-Colominas. (1975) 17, 1505
Niter [KNO <sub>3</sub> ]	PDF#81-0070	Lu, H.M., Hardy.(1991). 44, 7215

**1**  
 The final Rietveld scale factors were converted to PCs-by-weight using the “ZMV” expressions below:

$$\text{wt. \% (analyte phase)} = \frac{[s(ZMV)]_{\text{analyte phase}}}{\sum [s(ZMV)]_{\text{all phase}}} \quad (4)$$

**1**  
 where s, Z, M and V signify the phase scale factors; number of formula units/cell; formula weights and unit cell volumes, respectively.

**RESULTS**


**Bulk chemical compositions**

Chemical compositions of the crystal solid were analysed for major and trace elements. The chemical compositions are presented in the form of element weight percents, independent of the actual form of chemical binding in the residues. The light elements oxygen and carbon could not be analysed. However, the cations may be mainly bound in oxide compounds.

Table 2. Chemical elements of precipitating solids

Elements	P	Mg	K	Ca	Ni	Fe	Cu	Ti	Cr	Zn
Wt. %	61.9	12.0	9.8	8.5	4.3	1.2	0.7	0.6	0.3	0.2
Esd	1.4	2.0	0.1	0.4	0.3	0.1	0.1	0.1	0.1	0.0

**Powder XRD analysis**

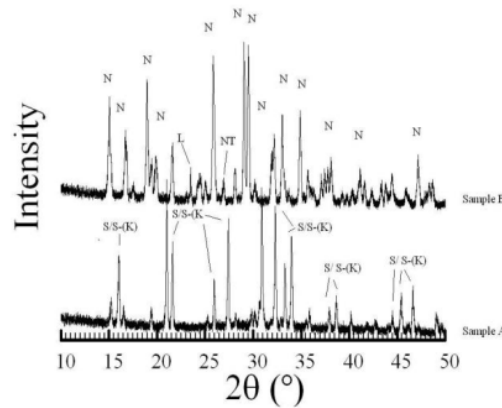

**Figure-1.** XRPD pattern of the samples A and B obtained at temperature of 30 °C and pH 10. The principal diffraction peaks of the predominant minerals are shown for reference purposes. The peaks are labelled L (lepidocrocite); N (newberyite); NT (niter); S (struvite), and S-(K) (struvite K).

**Table 3** Mineralogical phase composition of the synthetic materials using samples of A and B

Sample A			Sample B		
	wt. %	eds		wt. %	eds
Struvite-(K)	87.64	1.08	Newberyite	96.91	0.61
Struvite	12.36	0.88	Lepidocrocite	1.40	0.01
			Niter	1.69	0.04
Total	100.00		Total	100.00	


### DISCUSSIONS

Table 2 presents the chemical compositions of the crystal solid. The sum of the major components and trace element concentrations for these materials are notably less than 100 %, because the remainder of the materials may comprise largely water and carbon dioxide (which were not analysed for).

The mineralogy phases of crystal solid controlling the magnesium, ammonium, phosphate levels in the solution were initially identified by XRPD search-match method. In this method, all XRPD patterns of sample A agree well with the PDF#71-2089 value for struvite, and the DF#35-0812 value for struvite-(K), while PDF#70-2345 value for newberyite [MgHPO<sub>4</sub>•3H<sub>2</sub>O], PDF# 76-2301 value for lepidocrocite [FeOOH] and PDF#81-0070 value for niter [KNO<sub>3</sub>] were found in the sample B. The 'candidate and/or probable' minerals found in the search-match program were subsequently proved by the full profile Rietveld refinement, as peaks of phases which have been missed in the search match or mistakenly assigned phases clearly stand out in the difference plot of the calculated and the measured diffraction profile (Prince, 1993; Rietveld, 1969; Winburn *et al.*, 2000) (fig.1).

The quantitative results are given in weight percent normalised to 100 %. The major mineralogical phases in the sample A are struvite-(K) in addition to struvite. The significant amount of newberyite is obtained in the sample B with some minor of lepidocrocite and nitrite produced. This indicates that the use of different chemical grade in solution provided the different minerals, although the molar ratio is same. The highest purity of chemical powder has influenced the formation of struvite family crystals, but the lowest purity may be favoring in formation of newberyite crystals.

Both the struvite and struvite-(K) has been known to be iso-structural minerals [Graeser *et al.*, 2008]. The struvite-(K) precipitation may occur in the solution according to following reaction:




The presence of KOH in the solution may react to ions of Mg<sup>2+</sup> and PO<sub>4</sub><sup>3-</sup> to form struvite-(K). Here Mg<sup>2+</sup> ion was partly consumed for this mineral, while the rest of Mg ion may be used for struvite formation. Moreover, solution pH controls the distribution ammonia nitrogen between NH<sub>4</sub><sup>+</sup> and NH<sub>3</sub> according to following equilibrium reaction:



where the equilibrium constant (K<sub>a</sub>), is defined as [Stumm and Morgan, 1996].

$$K_a = \frac{[\text{NH}_3][\text{H}_3\text{O}^+]}{[\text{NH}_4^+]} = 5.7 * 10^{-10} \quad (7)$$

The high pH values have been reported to favor NH<sub>3</sub> formation which is in equilibrium with air according to Henry Law and promotes air stripping of ammonia [Stumm and Morgan, 1996]. At pH 10 examined during the study, much ammonia could be lost at 30 °C, resulting to the minor struvite formation. In contrast, newberyite was found in quite abundance in the sample B. Newberyite is known as a rare mineral and can be formed in the absence of ammonium. The absence of ammonium may be lost at the temperature studied. This mineral was subsequently precipitated out the solution according to the following reaction [Abbona *et al.*, 1979]:



The formation of this mineral is commonly accompanied by other phosphates (*e.g.* struvite and hannayite) [Abbona *et al.* 1988]. Here pH and molar ratio of MAP concentration are particularly an important parameter in the crystal formation and aggregation. The significant amount of newberyite was produced in the study, because this mineral can be developed significantly with MAP of 1:1:1 molar ratio [Abbona *et al.*, 1979].

## CONCLUSIONS

The study proved that the use of different purity of material in the synthesis of struvite provided the different minerals. Use of the technical grade material enables major struvite to form in the condition pH selected. In contrast, newberyite is the major mineral in the synthesis of material using the analytical grade chemical. As shown in Table 2 where certain hazardous substances such as Cu, Cr and Zn can also be shipped in the process of formation of struvite. It is also reinforced by the results shown in Table 3 where the purity of the chemical will affect the results struvite formed though the same molar ratios are used. The pH for ammonia recovery as struvite precipitation in the technical grade sample is 10. However, the same pH used in the analytical grade sample has experienced the loss of ammonia to air due to stripping since high pH favors NH<sub>3</sub>. Newberyite precipitation has also been observed as low as pH 10.

## Acknowledgements

The work was supported by the University of Pambangunan National, Surabaya Indonesia under the PhD research grant program.

## REFERENCES

Abbona F., Boistelle R., Haser R. (1979). Hydrogen bonding in MgHPO<sub>4</sub>·3H<sub>2</sub>O (newberyite). *Acta Crystallographica*, B35, 2514-2518.

Abdelrazig B.E.I., Sharp J.H. (1988). Phase changes on heating ammonium magnesium phosphate hydrates. *Thermochimica Acta* 129,197-215.

Abbona F., Lundager Madsen H. E., Boistelle R. (1988). The final phases of calcium and magnesium phosphates precipitated from solutions of high to medium concentration *J. Cryst. Growth*. 89, 592-602.

Battistoni P., Fava G., Pavan P., Musacco A., Cecchi F. (1997). Phosphate Removal in Anaerobic Liquors by Struvite Crystallization Without Addition of Chemicals: Preliminary Results, *Wat. Res.*, 31, 2925-2929.

Battistoni P., Pavan P., Prisciandaro M., Cecchi F. (2000). Struvite Crystallization: A feasible and reliable way to fix phosphorus in anaerobic supernatants, *Wat. Res.*, 34, 3033-3041.

Frost R.L., Weier M.L., Erickson K.L. (2004). Thermal decomposition of struvite, *J. Therm. Anal. Calorim.* 76,1025-1033.

Gaterell M.R., Gay R., Wilson R., Gochin R.J., Lester J.N. (2000). An economic and environmental evaluation of the opportunities for substituting phosphorus recovered from wastewater treatment works in existing UK fertiliser markets, *Env. Technol.*, 21, 1067-1084.

Graeser S., Wostl W., Bojar H.P., Berlepsch P., Armbruster T., Raber T., Ettinger K., Walter F. (2008). Struvite-(K), KMgPO<sub>4</sub>·6H<sub>2</sub>O, the potassium equivalent of struvite a new mineral. *European Journal of Mineralogy* 20, 629-633.

Lu H. M. and Hardy J. R. (1991). First-principles study of phase transitions in KNO<sub>3</sub>. *Physical Review. B* 44, 7215.

Loewenthal R.E., Kornmuller U.R.C., Van Heerden E.P. (1994). Struvite Precipitation in Anaerobic Treatment Systems, *In 17<sup>th</sup> International Symposium on Anaerobic Digestion, Capetown, South Africa*, 498-507.

Musvoto E. V., Wentzel M. C., Ekama G.A. (2000). Integrated Chemical-Physical Process Modeling-II. Simulation Aeration Treatment For Anaerobic Digester Supernatant. *Water Research*, 34, 1868 - 1880.

Pernet M., Joubert J.C., Berthet-Colominas C. (1975). Etude par diffraction neutronique de la forme haute pression de FeOOH, *Solid State Communications, Volume 17, Issue 12*, 15, Pages 1505-1510.

Priestley A.J., Cooney E., Booker N.A., Fraser I.H. (1997). Nutrients in wastewater - ecological problem or commercial opportunity. *Proceedings of the 17<sup>th</sup> Federal Convention of the Australian Water and Wastewater Association, Melbourne*, 1, 340-346.

Rodriguez-Carvajal J., Program Fullprof.2k, version 3.30, Laboratoire Leon Brillouin, France, June 2005.

Snoeying V.L., Jenkins D. (1980). *Water Chemistry*, John Wiley and Sons Inc., New York.

Sarkar A.K. (1991). Hydration/dehydration characteristics of struvite and dittmarite pertaining to magnesium ammonium phosphate cement systems. *J. Mater. Sci.*, 26, 2514-2518.

12

Schulze-Rettmer R. (1991). The Simultaneous Chemical Precipitation of Ammonium and Phosphate in the Form of Magnesium Ammonium Phosphate, *Water Sci. Technol.*, 23, 659-667

26

Stumm W., Morgan J.J. (1996). *Aquatic Chemistry*, Wiley-Interscience, New York .

27

Shin H.S., Lee S.M. (1997). Removal of Nutrients in Wastewater by Using Magnesium Salts, *Env. Technol.*, 19, 283-290.

15

Tünay O., Kabdasli I., Orhon D., Kolçak S. (1997). Ammonia removal by magnesium ammonium phosphate precipitation in industrial wastewaters, *Water Sci. Technol.*, 36, 225-228.

19

Whitaker A., Jeffery J.W. (1970) . The crystal structure of struvite,  $MgNH_4PO_4 \cdot 6H_2O$ . *Acta Crystallographica B*26,1429-1440.



# Synthesis and Characterisation

---

## ORIGINALITY REPORT

---

22%

SIMILARITY INDEX

6%

INTERNET SOURCES

19%

PUBLICATIONS

9%

STUDENT PAPERS

---

## PRIMARY SOURCES

---

- |   |   |    |
|---|---|----|
| 1 | <a href="http://www.icdd.com">www.icdd.com</a><br>Internet Source   | 1% |
| 2 | Submitted to University of Houston System<br>Student Paper  | 1% |
| 3 | Submitted to Universitas 17 Agustus 1945 Semarang<br>Student Paper  | 1% |
| 4 | Ashaki A. Rouff. "Temperature-dependent phosphorus precipitation and chromium removal from struvite-saturated solutions", Journal of Colloid and Interface Science, 2013<br>Publication | 1% |
| 5 | J. Chanona. "Application of a fuzzy algorithm for pH control in a struvite crystallisation reactor", Water Science & Technology, 06/2006<br>Publication                                 | 1% |
| 6 | Dominik Sidorczuk, Marcin Kozanecki, Bartolomeo Civalleri, Katarzyna Pernal, Jolanta Prywer. "Structural and Optical Properties of Struvite. Elucidating Structure of Infrared          | 1% |

Spectrum in High Frequency Range", The  
Journal of Physical Chemistry A, 2020

Publication

---

7

Submitted to ahknI

Student Paper

1%

---

8

Babic-Ivancic, V.. "Kinetics of struvite to newberyite transformation in the precipitation system  $MgCl_2-NH_4H_2PO_4-NaOH-H_2O$ ", Water Research, 200610

Publication

1%

---

9

L. Edahwati, S. Sutiyono, S. Muryanto, J. Jamari, A. P. Bayuseno. "THE EFFECT OF SUPERSATURATION CONTROL STRATEGY FOR PHOSPHATE RECOVERY THROUGH PRECIPITATION OF STRUVITE IN AN AIR-AGITATED COLUMN REACTOR", Rasayan Journal of Chemistry, 2018

Publication

1%

---

10

Submitted to Birla Institute of Technology and Science Pilani

Student Paper

1%

---

11

Battistoni, P.. "Phosphate removal in anaerobic liquors by struvite crystallization without addition of chemicals: Preliminary results", Water Research, 199711

Publication

1%

---

Gaétan Parent, Gilles Bélanger, Noura Ziadi,

12

Jean-Pierre Deland, Jean Laperrière.  
"Precipitation of Liquid Swine Manure  
Phosphates Using Magnesium Smelting By-  
Products", Journal of Environmental Quality,  
2007

Publication

1%

13

S. G. da Cruz, M. B. de M. Monte, A. J. B.  
Dutra. "Electroflotation of precipitated phosphate  
from synthetic solution", Brazilian Journal of  
Chemical Engineering, 2017

Publication

1%

14

Yu, Rongtai, Subin Cheng, Hongqiang Ren,  
Yanru Wang, Lili Ding, Jinju Geng, Ke Xu, and  
Yan Zhang. "Ammonium removal from  
wastewater via struvite pyrolysate recycling with  
Mg(OH)<sub>2</sub> addition", Water Science &  
Technology, 2013.

Publication

1%

15

Ebru Akkaya. "Post-treatment of anaerobically  
treated medium-age landfill leachate",  
Environmental Progress & Sustainable Energy,  
2009

Publication

1%

16

E. Boulard, M. Harmand, F. Guyot, G. Lelong,  
G. Morard, D. Cabaret, S. Boccato, A. D. Rosa,  
R. Briggs, S. Pascarelli, G. Fiquet. "Ferrous Iron  
Under Oxygen-Rich Conditions in the Deep

1%

---

17 Stuart Gatehouse, William Noble. "The Speech, Spatial and Qualities of Hearing Scale (SSQ)", International Journal of Audiology, 2009 1%

Publication

---

18 S. Vichaphund, W. Intiya, A. Kongkaew, S. Loykulnant, P. Thavorniti. "Utilization of sludge waste from natural rubber manufacturing process as a raw material for clay-ceramic production", Environmental Technology, 2012 1%

Publication

---

19 rruff.info 1%

Internet Source

---

20 link.springer.com 1%

Internet Source

---

21 V. Babić-Ivančić, J. Kontrec, L. Brečević. "Formation and transformation of struvite and newberyite in aqueous solutions under conditions similar to physiological", Urological Research, 2004 1%

Publication

---

22 www.mdpi.com 1%

Internet Source

---

23 repository.ubaya.ac.id <1%

Internet Source

---

24

He. "Characteristics and origin of underpressure system in the Shiwu Fault Depression, south-east Songliao Basin, China", Basin Research, 6/2000

Publication

<1%

25

H.H. Tran, F.A. Roddick. "Comparison of chromatography and desiccant silica gels for the adsorption of metal ions. II. Fixed-bed study", Water Research, 1999

Publication

<1%

26

Submitted to University of Bedfordshire

Student Paper

<1%

27

Shih, K., and H. Yan. "The Crystallization of Struvite and Its Analog (K-Struvite) From Waste Streams for Nutrient Recycling", Environmental Materials and Waste, 2016.

Publication

<1%

28

[linknovate.com](http://linknovate.com)

Internet Source

<1%

29

Dione Mari Morita, Renan de Luca Avila, Fernando Ngan Aidar. "Nucleação na formação de estruvita: estado da arte", Engenharia Sanitaria e Ambiental, 2019

Publication

<1%

30

Koichi Toyoda. "Bibliography of ferroelectrics", Ferroelectrics, 2000

Publication

<1%

31

Ma, Ning, Ashaki A. Rouff, and Brian L. Phillips. "A  $^{31}\text{P}$  NMR and TG/DSC-FTIR Investigation of the Influence of Initial pH on Phosphorus Recovery as Struvite", ACS Sustainable Chemistry & Engineering, 2014.

Publication

---

<1%

32

Jinru Lin, Ning Chen, Yuanming Pan. " Arsenic Incorporation in Synthetic Struvite ( $\text{NH}_4\text{MgPO}_4 \cdot 6\text{H}_2\text{O}$ ): A Synchrotron XAS and Single-Crystal EPR Study ", Environmental Science & Technology, 2013

Publication

---

<1%

---

Exclude quotes Off

Exclude matches Off

Exclude bibliography Off